Machinability

◆Endmilling

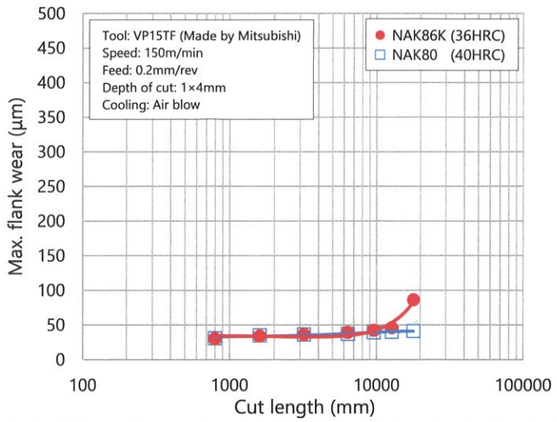

◆Drilling

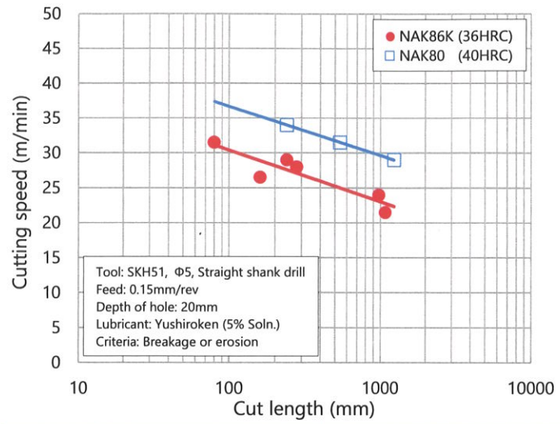

Physical Properties

	Unit	25°C	100°C	200°C	300°C
Thermal conductivity	W/m・K	27.5	29.2	29.3	29.6
Specific heat	J/kg・K	484	529	550	583

	Unit	20-100°C	20-200°C	20-300°C
Thermal expansion rate	$x10^{-6}$/K	9.8	10.6	11.0

Build-up Welding Method

◆**Build-up welding procedure (recommendation)**

1. Preparation
   ・Fully clean all oils, foreign material, and scales.
   ・Remove all cracks and surface treatment layers.
   ・Beveling: corner sections 3R or above.
2. Build-up Welding Rod
   ・NAK86K
3. Welding
   ・DC normal polarity, backward welding.
4. Precautions
   ・If pre-heating and post-heating are conducted with a burner, the entire body should be heated to prevent cracking.
   ・Pre-heating and post-heating is not necessary when build-up welding is very small. When welding in large quantities, pre-heating (300-350°C) and post-heating (400-450°C) is recommended.
   ・Even if there is no problem when welding without post-heating, since there is a concern of cracking due to welding stress, post-heating is recommended.

【Precaution for Use】
NAK86K has various features as plastic mold steel, but some features are different from NAK80.
Should you have any questions or require additional information, please contact the following addresses.

DAIDO STEEL

Tokyo Head Office
(Tool Steel Div. Tool Steel Marketing & Sales Dept. Overseas Sect.)
Daido Shinagawa Building, 6-35, 1-Chome, Konan, Minato-ku, Tokyo, Japan
Phone: +81-3-5495-1270 Fax: +81-3-5495-6739

Bangkok Office
Unit2-1, 22nd Fl., Silom Complex Bldg., 191, Silom Road, Silom, Bangrak, Bangkok 10500, Thailand
Phone: +66-2-231-3214 Fax: +66-2-231-3216

Daido Steel Group Europe GmbH
Insterburger Strasse 16, 60487 Frankfurt am Main, Germany
Phone: +49-69-29802867-0 Fax: +49-69-29802867-40

Daido Steel (America) Inc.
1051 Perimeter Drive, Suite 1175, Schaumburg, Illinois 60173, U.S.A.
Phone: +1-847-517-7950 Fax: +1-847-517-7951

Daido Steel (Shanghai) Co., Ltd
Room 1402, Ruijin Building, 205 Mao Ming Nan Road, Shanghai, 200020, China
Phone: +86-21-5466-2020 Fax: +86-21-5466-0279

Daido Steel (Shanghai) Co., Ltd Guangzhou Subsidiary Company
Room 2601, No.8, Linhezhoug Road, Tianhe District, Guangzhou, 510610, China
Phone: +86-20-3877-1632 Fax: +86-20-8550-1126

www.daido.co.jp

NAK is a Registered trademark or Trademark of Daido Steel Co., Ltd.

■Document Disclaimer
The product characteristics included in this brochure are the representative values based on the result of our measurements, and do not guarantee the performance in use of the products.
Please inquire the latest information to our department in charge as the information of this brochure is updated without previous notice as needed.
Copyright ©2020 Daido Steel Co., Ltd. All rights reserved.

No.SC1908 20.10.0,5 (DDD)

Daido's Plastic Mold Steel Series

NAK86K™

Pre-hardened type plastic mold steel with excellent corrosion resistance and toughness.

Features

◆Improved corrosion resistance makes it possible to solve NAK80 molds' rust troubles.

◆Effective as countermeasure for cracking of molds made out of NAK80 or SUS420J2 because of its high toughness at molding temperature.

◆Excellent cleanliness by remelting makes it possible to have excellent mirror polishability equivalent to NAK80.

◆Direct machining is possible because NAK86K is pre-hardened with uniform hardness of 35-38HRC.

Conceptual Diagram of NAK86K

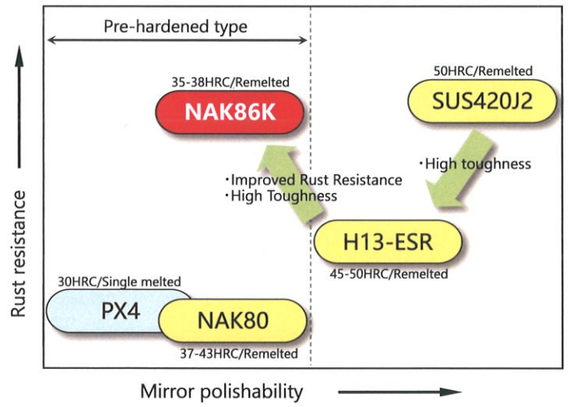

NAK86K and NAK80 Feature Comparison

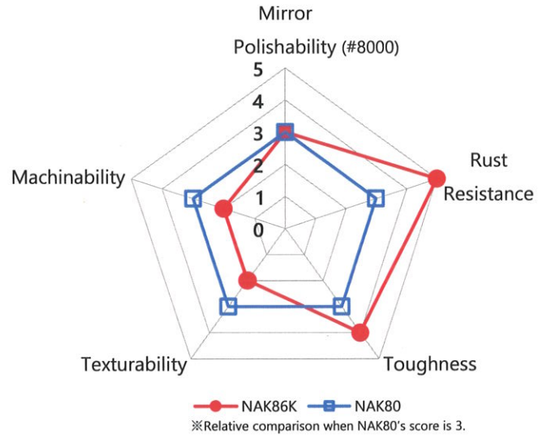

<Difference from NAK80>
◇Since NAK86K has better corrosion resistance than NAK80, caution is necessary when texturing process is applied.
◇NAK86K is hardened and tempered steel, thus it needs more removal allowance for rough machining than NAK80.

Chemical Composition

Daido Brand	Supplied Condition (Hardness)	Chemical Composition (%)						
		C	Si	Mn	Ni	Cr	Mo	V
NAK86K	Pre-hardened (35-38HRC)	Low C-8%Cr						

DAIDO STEEL

Properties

Material size：260H×610W×260L

Mirror Polishability (#8000)

◆NAK86K mirror polishability is equivalent to NAK80.

NAK86K (36HRC)

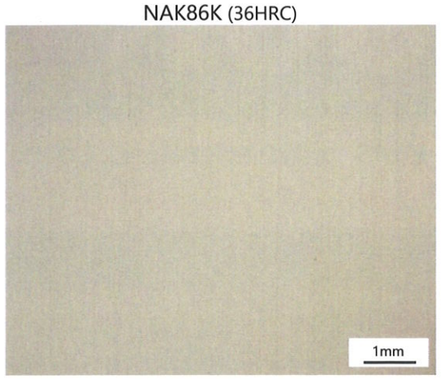

NAK80 (40HRC)

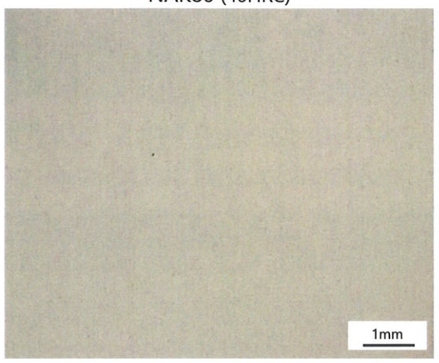

＜Polishing procedure＞
Carbon grinding (#1500-#3000) → Emery paper polishing (#1500-#2000-#2500) → Diamond paste finishing (#1800-#3000-#8000)

Texturability

◆NAK86K is capable of being textured, but texture conditions are different from NAK80.

※Please ask texturing condition to texture processors.

Satin Pattern

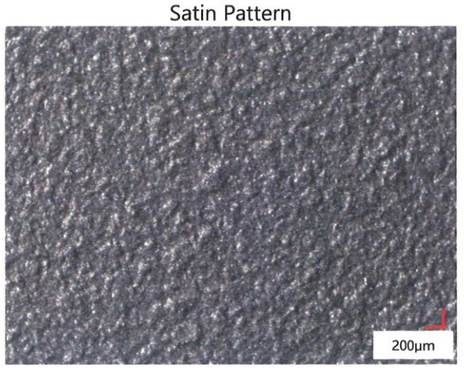

Leather Pattern

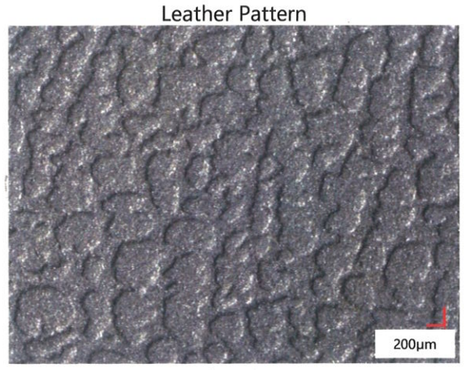

Texture processing: TANAZAWA HAKKOSHA Co., Ltd.

Rust Resistance

◆NAK86K has better rust resistance than NAK80.

NAK86K (36HRC) | NAK80 (40HRC) | SUS420J2 (37HRC)

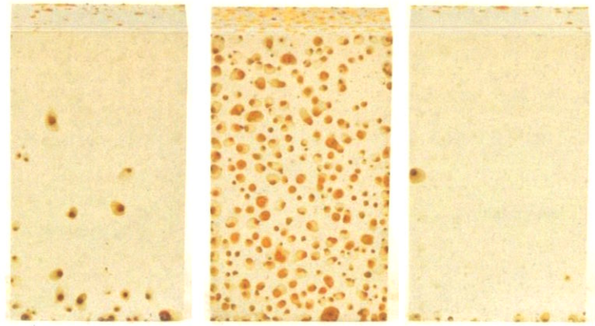

＜Wetting test condition＞Temp. 50°C, Humidity 98%, Time 48h

Corrosion Resistance

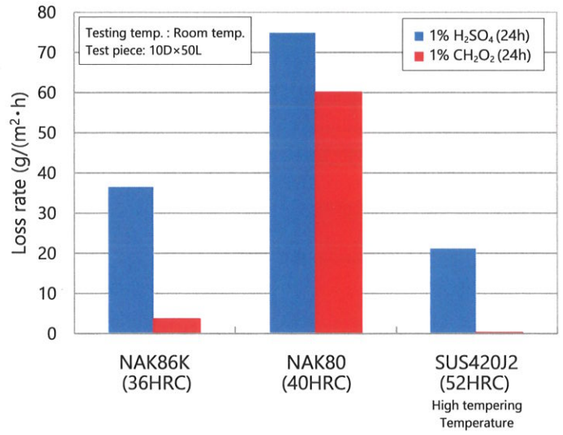

Nitriding Characteristics

◆Nitriding can be applied to NAK86K. ※Please process at 500°C or lower to prevent softening.

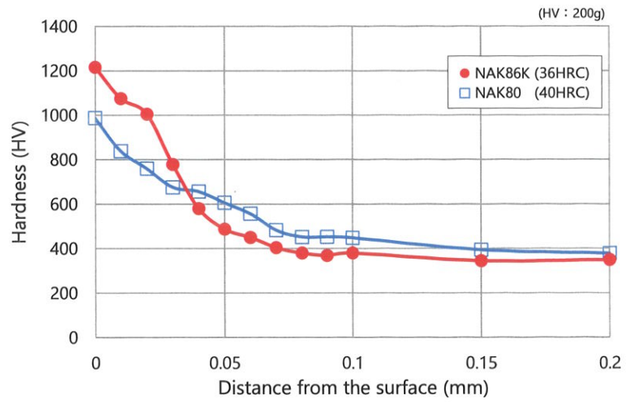

NAK86K

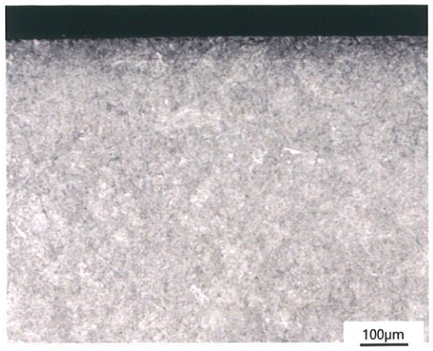

Nitriding process: LICHTSEIKO Inc. EDISON HARD PROCESS (Plastic mold specification)

Mechanical Properties

◆Toughness

	Testing temp.	Hardness (HRC)	Toughness (J/cm²)
SUS420J2 (Remelted)	Room temp.	53	Approx. 25
NAK80	Room temp.	40	Approx. 25
NAK86K	Room temp.	36	Approx. 30-150
	100°C※	36	≧Approx. 150

・Direction: L direction
・Test piece: 2mmU Notched

※Simulating molding temperature of 100°C

◆Tensile strength

	NAK86K (36HRC)
0.2% Proof stress (MPa)	880
Tensile strength (MPa)	1200

・Test piece: JIS No.14
・Direction: L direction
・Testing temp. : Room temp.

Weldability

◆TIG welding (Welding rod: Φ1.0mm)

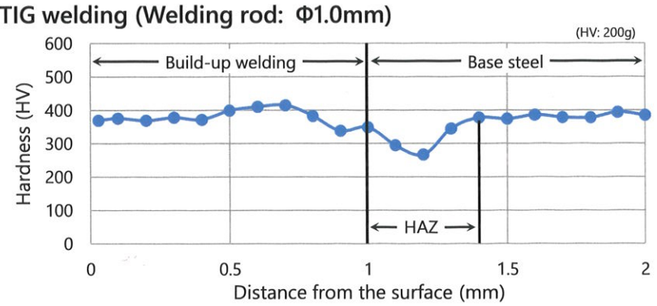

＜Welding conditions＞
・Test piece dimension: groove angle 90°×depth 1mm
・Welding rod: NAK86K
・Current: 100A
・Shield gas: Argon
・Gas flow rate: 1.8L/min

Weld test piece shape

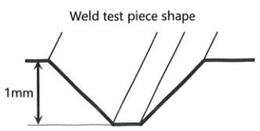

◆Surface condition after TIG welding
(No pre-heating and post-heating)

After mirror polishing (#8000)

Welding area